

Evaluation of the effects of two novel irrigants on intraradicular dentine erosion, debris and smear layer removal

Melihat Görduysus^{1,2},
Selen Küçükkaya^{1*},
Nursel Pekel Bayramgil³,
Mehmet Ömer
Görduysus^{1,4}

¹Department of Endodontics, Faculty of Dentistry, Hacettepe University, Ankara, Turkey

²RAK College of Dental Science, RAK Medical and Health Science University, Ras Al Khaimah, UAE

³Chemistry Department, Faculty of Science, Hacettepe University, Ankara, Turkey

⁴Department of Endodontics, Sharjah University Dental College, Sharjah, UAE

Received March 15, 2015;
Accepted April 8, 2015.

¹Görduysus M; Küçükkaya S; Görduysus MÖ, Department of Endodontics, Faculty of Dentistry, Hacettepe University, Ankara, Turkey

²Görduysus M, RAK College of Dental Science, RAK Medical and Health Science University, Ras Al Khaimah, UAE

³Bayramgil NP, Chemistry Department, Faculty of Science, Hacettepe University, Ankara, Turkey

⁴Görduysus MÖ, Department of Endodontics, Sharjah University Dental College, Sharjah, UAE

*Correspondence to

Selen Küçükkaya, DDS, PhD.
Research Assistant, Department of Endodontics, Hacettepe University Faculty of Dentistry, 06100, Sıhhiye, Ankara, Turkey
TEL, +90-312-305-2260; FAX, +90-312-310-4440; E-mail, selenkkaya@yahoo.com


Objectives: To evaluate the effects of copolymer of acrylic acid and maleic acid (Poly[AA-co-MA]) and calcium hypochlorite (Ca(OCl)₂) on root canal dentin using scanning electron microscope (SEM). **Materials and Methods:** Twenty-four single-rooted teeth were instrumented and the apical and coronal thirds of each root were removed, leaving the 5 mm middle thirds, which were then separated into two pieces longitudinally. The specimens were randomly divided into six groups and subjected to each irrigant for 5 min as follows: G1, Ca(OCl)₂; G2, Poly(AA-co-MA); G3, Ca(OCl)₂ + Poly(AA-co-MA); G4, sodium hypochlorite (NaOCl); G5, ethylenediaminetetraacetic acid (EDTA); G6, NaOCl+EDTA. The specimens were prepared for SEM evaluation. Smear layer, debris and erosion scores were recorded by two blinded examiners. One image from G3 was analyzed with energy dispersive spectroscopy (EDS) on suspicion of precipitate formation. Data were analyzed using the Kruskal-Wallis and Dunn tests. **Results:** G1 and G4 showed the presence of debris and smear layer and they were statistically different from G2, G3, G5 and G6 where debris and smear layer were totally removed ($p < 0.05$). In G1 and G4, erosion evaluation could not be done because of debris and smear layer. G2, G3 and G5 showed no erosion, and there was no significant difference between them. G6 showed severe erosion and was statistically different from G2, G3 and G5 ($p < 0.05$). EDS microanalysis showed the presence of Na, P, and Ca elements on the surface. **Conclusions:** Poly(AA-co-MA) is effective in removing the smear layer and debris without causing erosion either alone or with Ca(OCl)₂. (*Restor Dent Endod* 2015;40(3):216-222)

Key words: Acrylic acid; Calcium hypochlorite; Dentin; Maleic acid

Introduction

The major goal of root canal treatment is to eliminate microorganisms and remove inflamed or necrotic organic tissue.¹ Several studies have shown that mechanical instrumentation alone is not able to reduce the microbial population in the root canal system.²⁻⁴ Furthermore, a nonhomogeneous structure, called the smear layer, is formed on dentin surface by the mechanical action of the instruments.⁵ This layer is comprised of inorganic and organic substances such as fragments of odontoblastic processes, microorganisms, and necrotic tissue.⁶ The removal of the smear layer could contribute to the disinfection of the root canal system and improve the seal of the root canal filling.⁷ Therefore, to effectively clean and disinfect the root canal system, irrigation is an essential part of root canal treatment.⁸

Sodium hypochlorite (NaOCl) solutions are the most widely recommended irrigants in endodontics with regards to their good antimicrobial efficacy and unique capacity to dissolve organic tissue remnants.⁸ On the other hand, NaOCl is cytotoxic and can cause local tissue necrosis in case of extrusion to the periapical area.⁹ Therefore, there have been attempts to identify alternative irrigants with the same efficacy as NaOCl, but less toxicity.¹⁰ Calcium hypochlorite ($\text{Ca}(\text{OCl})_2$) is a powder that is chemically similar to NaOCl, and it is a chlorine source, which forms hypochlorous acid as twice as NaOCl and calcium hydroxide ($\text{Ca}(\text{OH})_2$) when mixed with water. $\text{Ca}(\text{OCl})_2$ is as widely used as NaOCl for water treatment and as a bleaching agent. To date, only one study evaluated its application in endodontics, and it was found to be as efficient as NaOCl for dissolving organic tissue.¹¹ However, since the smear layer has an inorganic component as well, calcium chelators are used with NaOCl in root canal treatment to ensure its complete removal.¹² Ethylenediaminetetraacetic acid (EDTA) has a long-standing history as a chelator agent in endodontics. However, researchers have reported its potential to cause irritation.^{13,14} In addition, several reports have indicated that the sequential use of EDTA and NaOCl may lead to dentinal erosion on the root canal wall.^{15,16} A copolymer of acrylic acid and maleic acid (poly[AA-co-MA]) is a chelator that is obtained by radical copolymerization of maleic anhydride (MA) with acrylic comonomers. In the literature, many data can be found regarding the application of MA copolymers in the medical and pharmaceutical fields. This copolymer is considered to be biocompatible with good chelating properties, and it has the following formula:¹⁷

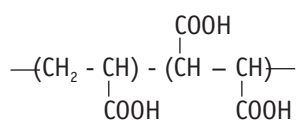

The purposes of this study were to evaluate poly(AA-co-MA) and $\text{Ca}(\text{OCl})_2$ in removing the smear layer and debris and to investigate their erosive effects on the root canal wall using scanning electron microscope (SEM).

Materials and Methods

Preparation of the materials

The materials used were 7% $\text{Ca}(\text{OCl})_2$ (Sigma-Aldrich Chemie GmbH, Steinheim, Germany), 25% Poly(AA-co-MA) (Aldrich Chemical Co., Milwaukee, WI, USA), 17% EDTA (Vista Dental Products, Racine, WI, USA) and 2.5% NaOCl. $\text{Ca}(\text{OCl})_2$ solution was freshly prepared by dissolving 25 g $\text{Ca}(\text{OCl})_2$ granules in 75 mL of deionized water, and then gravimetrically analyzed to determine the exact mass ratio. This stock solution was used after dilution to 7% $\text{Ca}(\text{OCl})_2$. Poly(AA-co-MA) (50 wt% solution in water, pH = 1)

was diluted to 25% with distilled water.

Selection and preparation of the specimens

This study was revised and approved by the Ethics Committee of Hacettepe University (Project No., GO 13/364). Twenty-four single-rooted human teeth with a single canal were used in this study. The teeth were decoronated at the cemento-enamel junction with a diamond bur. Each root canal was negotiated with a size 10 K-file (Dentsply Maillefer, Ballaigues, Switzerland) and the working length (WL) was calculated by subtracting 0.5 mm from this length. Size 15 and 20 K-files (Dentsply Maillefer) were used at the WL and any root with an apical constriction diameter wider than a size 20 file was excluded. Thereafter, ProTaper rotary instruments (Dentsply Tulsa Dental Products, Tulsa, OK, USA) were used in continuous clockwise rotation using a gentle in-and-out motion. SX was used at two thirds of the WL, then Shaping Files 1 and 2 (S1 and S2) and the Finishing Files 1 through 3 (F1 - F3) at the WL with circumferential filing to touch all surfaces. Each set of instruments was used to enlarge 2 canals only. All preparations were performed by one operator. The root canals were irrigated with distilled water between each instrument. After instrumentation, the apical and coronal thirds of each root were removed with carborundum discs. Two longitudinal grooves were prepared on the buccal and lingual surfaces without exposing the root canals. Thereafter, the 5 mm middle third sections were split into two equal pieces with a hammer and chisel.

Distribution of specimens and final irrigation

Forty-eight samples were randomly divided into 6 groups and subjected to the irrigants as described in Table 1. A total volume of 2 mL of each irrigant was used for each specimen. A final flush was done with 2 mL of distilled water in all samples. In combination groups, 2 mL mid-irrigation with distilled water was applied to prevent possible interaction between the solutions. Each irrigant was applied for 5 minutes.

Table 1. Protocols for irrigation

Group	Irrigant
G1 (n = 8)	7% $\text{Ca}(\text{OCl})_2$
G2 (n = 8)	25% Poly(AA-co-MA)
G3 [#] (n = 8)	7% $\text{Ca}(\text{OCl})_2$ + 25% Poly(AA-co-MA)
G4 (n = 8)	2.5% NaOCl
G5 (n = 8)	17% EDTA
G6 [#] (n = 8)	2.5% NaOCl + 17% EDTA

[#]Represents combination groups.
EDTA, Ethylenediaminetetraacetic acid.

SEM examination

After irrigation procedures, the specimens were kept in an incubator at 37°C, then mounted on stubs, gold-sputtered and examined with SEM (JSM-6400, JEOL Ltd., Tokyo, Japan) at magnification of $\times 300$, $\times 1,000$ and $\times 3,000$. It is well known that SEM evaluation is subjective and qualitative, as the selection of the observation area is directly operator-dependent. Thus, to standardize the examined area for each sample, we applied the technique described by Paque *et al.*¹⁸ For this purpose, the central beam of the SEM was directed to the center of the specimen under $\times 10$ magnification, and the magnification was increased gradually to $\times 3,000$. The area of the canal wall captured on the screen of the SEM was used for scoring the sample.

The scores and scales of the presence of debris, smear layer and degree of erosion of dentinal tubules were presented in Table 2.^{19,20} The scoring was done by two independent examiners. When a difference occurred in the scoring of an image, the two examiners reevaluated the image and discussed it until an agreement was obtained. One image was analyzed with energy dispersive spectroscopy (EDS) on suspicion of precipitate formation.

Statistical analysis

All data were submitted to the Statistical Package for the SPSS for Windows 11.0 (SPSS Inc., Chicago, IL, USA). The results were statistically analyzed using the Kruskal-Wallis and Dunn tests at a significance level of $p < 0.05$.

Results

The smear layer, debris and erosion scores are presented in Table 3. G1 and G4 showed the presence of debris, and heavy smear layer and there was no significant difference between them (Figure 1). The smear layer and debris

Table 3. The smear layer, debris and erosion scores of each group

Group	Smear layer	Debris	Erosion
G1	4.5 \pm 0.534	4.625 \pm 0.517	N/A
G2	1.125 \pm 0.353	1.125 \pm 0.353	1
G3	1.125 \pm 0.353	1	1
G4	4.625 \pm 0.517	4.5 \pm 0.534	N/A
G5	1.125 \pm 0.353	1.125 \pm 0.353	1
G6	1.125 \pm 0.353	1	2.75 \pm 0.462

The values are expressed as mean \pm SD. N/A, Not Applicable.

Table 2. The scores and scales of the presence of debris, smear layer and degree of erosion of dentinal tubules

Score	Definition
The presence of debris evaluated with a scale of five scores ¹⁹	
1	Clean root canal wall and only a few small debris particles
2	A few small agglomerations of debris
3	Many agglomerations of debris covering less than 50% of the root canal wall
4	More than 50% of the root canal walls were covered with debris
5	Complete or nearly complete root canal wall coverage with debris
The presence of smear layer evaluated with a scale of five scores ¹⁹	
1	No smear layer, and all dentinal tubules were open
2	A small amount of smear layer, and some dentinal tubules were open
3	Homogeneous smear layer covering the root canal wall, and only a few dentinal tubules open
4	Complete root canal wall covered by a homogeneous smear layer, and no open dentinal tubules were observed
5	Heavy, homogeneous smear layer covering the complete root canal wall
The degree of erosion of the dentinal tubules evaluated with a scale of three scores ²⁰	
1	No erosion (all tubules were normal in appearance and size)
2	Moderate erosion (peritubular dentin was eroded)
3	Severe erosion (intertubular dentin was destroyed, and tubules were connected)

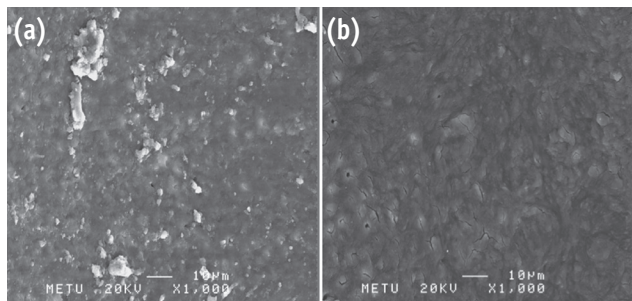


Figure 1. Photomicrographs showing the presence of debris and smear layer. (a) G1; (b) G4 (Bar = 10 μm; original magnification, x1,000).

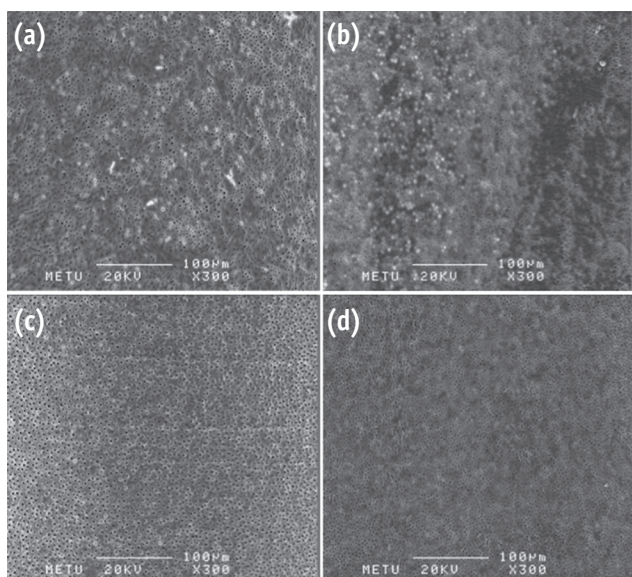


Figure 2. Photomicrographs showing the smear-free surfaces. (a) G2; (b) G3; (c) G5; (d) G6 (Bar = 100 μm; original magnification, x300).

were totally removed in G2, G3, G5 and G6 (Figure 2). The results indicated that G1 and G4 were statistically different from the remaining groups in removing debris and smear layer ($p < 0.05$). In G1 and G4, scoring for erosion could not be done because of the presence of debris and heavy smear layer. G2, G3 and G5 did not show any erosion, and there was no significant difference between them (Figure 3). G6 showed severe erosion and was statistically different from G2, G3 and G5 ($p < 0.05$, Figure 4). EDS microanalysis of a sample from G3 showed the presence of Na, P, and Ca elements on the surface of suspected precipitate (Figure 5).

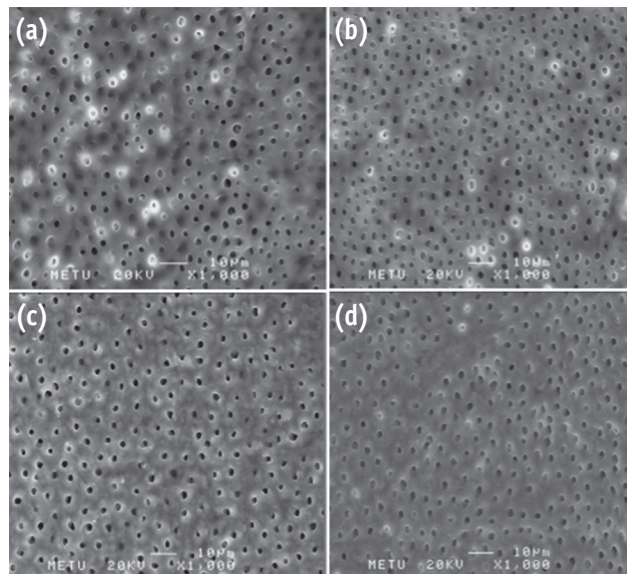


Figure 3. Representative photomicrographs for erosion evaluation. No erosion is present in (a) G2; (b) G3; (c) G5. Moderate erosion can be seen in (d) G6 (Bar = 10 μm; original magnification, x1,000).

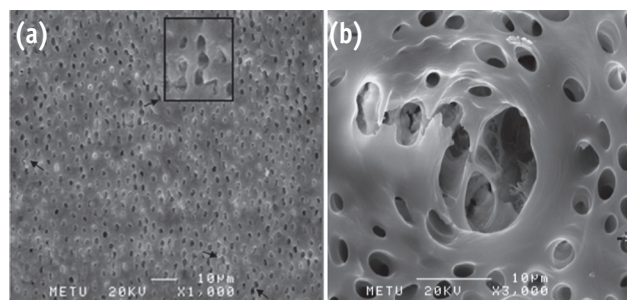


Figure 4. Representative photomicrographs of G6 showing severe erosion. (a) Bar = 10 μm, original magnification, x1,000; (b) Bar = 10 μm, original magnification, x3,000.

Discussion

While there are no evidence-based studies that provide outcomes of treatment based solely on the removal of the smear layer, it seems reasonable to suggest that removal of the smear layer can result in a more thorough disinfection of the root canal system and the dentinal tubules, which would ensure a better adaptation between the obturation materials and the root canal walls.⁷ Several studies have shown that the use of a combination of sodium hypochlorite (2.5 - 5%) and EDTA (10 - 17%) is particularly

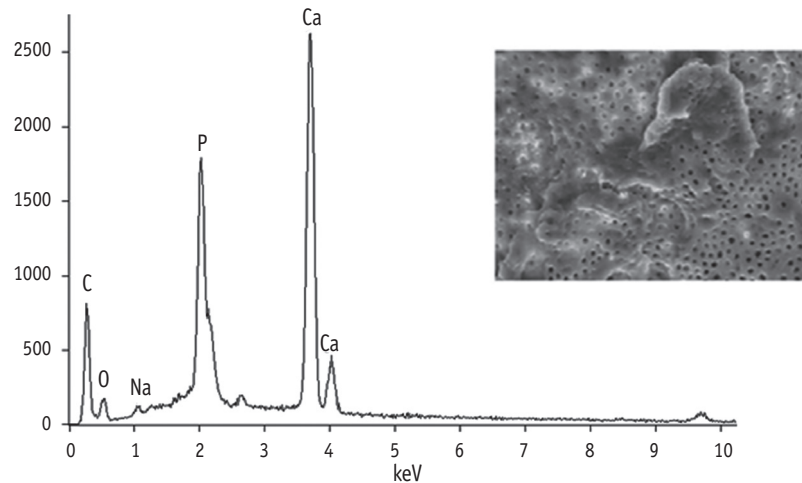


Figure 5. EDS microanalysis of a sample from G3.


effective in the removal of smear layer and debris.^{15,21,22} However, recent research seems to demonstrate an excessively aggressive effect of this combination on the root canal walls that could cause too much erosion and degradation of the dentin.^{7,15,23} Although its effect on the long-term success of endodontic treatment remains unclear, erosion could result in an alteration of mechanical properties of dentin and create more difficulties in the adaptation of the root filling materials to the canal walls.^{24,25}

It is a well-established point that the smear layer is created only where the endodontic instruments cut the dentinal walls effectively.²⁶ On the other hand, with both rotary nickel-titanium instruments and traditional stainless-steel hand instruments almost half of the root canal walls are left uninstrumented.^{18,27} This can become an issue when examining a surface that belongs to a smear-free area. The reason of this issue is that the smear-free area could be produced by the chelating solution or it may merely indicate an uninstrumented area.²⁶ This situation may cause inaccurate results in SEM examinations. In order to eliminate any potential problems that may develop due to uninstrumented areas, we chose to use 5 mm mid-roots in the present study, because it was reported previously that there is less untouched surface in the middle third of the root after root canal preparation.²⁸ Furthermore, this laboratory study was aimed to analyze the effects of two novel irrigants on dentin structures. Therefore, to ensure a uniform and direct contact of each irrigant with the root canal walls, final irrigations were performed after 5 mm mid-roots were divided into two pieces longitudinally. Although this approach does not represent the clinical situation, it is a useful method when evaluating the effects of a potential irrigant on dentin surface regardless of any canal variations.

A review of irrigation in endodontics revealed that optimal irrigation is commonly achieved by combining two or more irrigant solutions in a specific sequence.⁸ However, there is a concern that combined irrigation regimens may cause undesirable interactions between irrigants such as creation of erosion, loss of activity and development of potentially toxic by-products.²⁹ To avoid such interactions, we used distilled water between two irrigants in each of the combination groups. Nevertheless, we found that EDTA and NaOCl caused erosion around dentinal tubules in 5 minutes when used sequentially, whereas no erosion was observed in the combination group of novel irrigants. Although we used distilled water between irrigants, it was found that some precipitate can occur even when distilled water is used between the specific irrigants.²⁹ Therefore we considered this fact in the present study, as the tested materials were novel irrigants, and only one specimen from the combination group of novel irrigants showed an unusual view on its surface and was analyzed further with EDS. According to the analysis Na, P, and Ca elements which are the components of dentin were detected in the area indicating no chemical precipitate. More studies are required to examine whether a precipitate occurs in the contact of these two novel irrigants.

Poly(AA-co-MA) is a polymer with numerous applications for biomedical purposes. Their applications as drugs, drug-conjugates, enzyme-conjugates or gene delivery systems are also reported.¹⁷ It was reported that in pharmaceutical forms, poly(AA-co-MA) was able to improve mucosal permeability by its chelating abilities similar to EDTA.³⁰ According to our results, this copolymer demonstrated promising results as a novel and potential irrigant. Poly(AA-co-MA) produced entirely clean surfaces without damaging the dentinal surface when it was used alone or combined with $\text{Ca}(\text{OCl})_2$. Our results also showed that

$\text{Ca}(\text{OCl})_2$ was ineffective in removing the smear layer, which was also the same for NaOCl. The inability of NaOCl to dissolve the inorganic structures has been well documented in the literature.⁸ Considering the similar chemistry of these two chlorine products, our study also indicated that $\text{Ca}(\text{OCl})_2$ was ineffective on inorganic structures. On the other hand, a recent study concluded that $\text{Ca}(\text{OCl})_2$ was as effective as NaOCl in dissolving organic tissues, but with a slower rate which could contribute less tissue irritation in cases of periapical extrusion.¹¹ When NaOCl and $\text{Ca}(\text{OCl})_2$ are mixed with water the following reactions occur:



$\text{Ca}(\text{OH})_2$ and the higher generation of hypochlorous acid may enhance the antimicrobial efficacy of $\text{Ca}(\text{OCl})_2$. Furthermore, its effect on organic tissue makes it a potential root canal irrigant.¹¹ However, many aspects of this irrigant, such as its antimicrobial effectiveness, cytotoxicity and the interactions with other root canal irrigants should be investigated.

Conclusions

Poly(AA-co-MA) is effective in removing the smear layer and debris without causing erosion either alone or with $\text{Ca}(\text{OCl})_2$. Both irrigants have the potential to be used as irrigants in endodontics. More studies are necessary to further investigate the properties of these two novel irrigants.

Conflict of Interest: No potential conflict of interest relevant to this article was reported.

References

- Schilder H. Cleaning and shaping the root canal. *Dent Clin North Am* 1974;18:269-296.
- McComb D, Smith DC. A preliminary scanning electron microscopic study of root canals after endodontic procedures. *J Endod* 1975;1:238-242.
- Peters OA, Schönenberger K, Laib A. Effects of four Ni-Ti preparation techniques on root canal geometry assessed by micro computed tomography. *Int Endod J* 2001;34:221-230.
- Goldman LB, Goldman M, Kronman JH, Lin PS. The efficacy of several irrigating solutions for endodontics: a scanning electron microscopic study. *Oral Surg Oral Med Oral Pathol* 1981;52:197-204.
- McComb D, Smith DC, Beagrie GS. The results of *in vivo* endodontic chemomechanical instrumentation-a scanning electron microscopic study. *J Br Endod Soc* 1976;9:11-18.
- Gwinnett AJ. Smear layer: morphological considerations. *Oper Dent Suppl* 1984;3:2-12.
- Torabinejad M, Handysides R, Khademi AA, Bakland LK. Clinical implications of the smear layer in endodontics: a review. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2002;94:658-666.
- Zehnder M. Root canal irrigants. *J Endod* 2006;32:389-398.
- Becking AG. Complications in the use of sodium hypochlorite during endodontic treatment. Report of three cases. *Oral Surg Oral Med Oral Pathol* 1991;71:346-348.
- Cobankara FK, Ozkan HB, Terlemez A. Comparison of organic tissue dissolution capacities of sodium hypochlorite and chlorine dioxide. *J Endod* 2010;36:272-274.
- Dutta A, Saunders WP. Comparative evaluation of calcium hypochlorite and sodium hypochlorite on soft-tissue dissolution. *J Endod* 2012;38:1395-1398.
- Mader CL, Baumgartner JC, Peters DD. Scanning electron microscopic investigation of the smeared layer on root canal walls. *J Endod* 1984;10:477-483.
- Sceiza MF, Daniel RL, Santos EM, Jaeger MM. Cytotoxic effects of 10% citric acid and EDTA-T used as root canal irrigants: an *in vitro* analysis. *J Endod* 2001;27:741-743.
- Segura-Egea JJ, Jiménez-Rubio A, Rios-Santos JV, Velasco-Ortega E, Calvo-Gutierrez JR. *In vitro* inhibitory effect of EGTA on macrophage adhesion: endodontic implications. *J Endod* 2003;29:211-213.
- Baumgartner JC, Mader CL. A scanning electron microscopic evaluation of four root canal irrigation regimens. *J Endod* 1987;13:147-157.
- Calt S, Serper A. Smear layer removal by EGTA. *J Endod* 2000;26:459-461.
- Popescu I, Suflet DM, Pelin IM, Chitanu GC. Biomedical applications of maleic anhydride copolymers. *Revue Roumaine de Chimie* 2011;56:173-188.
- Paqué F, Barbakow F, Peters OA. Root canal preparation with Endo-Eze AET: changes in root canal shape assessed by micro-computed tomography. *Int Endod J* 2005;38:456-464.
- Hülsmann M, Rummelin C, Schäfers F. Root canal cleanliness after preparation with different endodontic handpieces and hand instruments: a comparative SEM investigation. *J Endod* 1997;23:301-306.
- Torabinejad M, Khademi AA, Babagoli J, Cho Y, Johnson WB, Bozhilov K, Kim J, Shabahang S. A new solution for the removal of the smear layer. *J Endod* 2003;29:170-175.
- Goldman M, Goldman LB, Cavaleri R, Bogis J, Lin PS. The efficacy of several endodontic irrigating solutions: a scanning electron microscopic study: Part 2. *J Endod*

- 1982;8:487-492.
22. Yamada RS, Armas A, Goldman M, Lin PS. A scanning electron microscopic comparison of a high volume final flush with several irrigating solutions: Part 3. *J Endod* 1983;9:137-142.
 23. Niu W, Yoshioka T, Kobayashi C, Suda H. A scanning electron microscopic study of dentinal erosion by final irrigation with EDTA and NaOCl solutions. *Int Endod J* 2002;35:934-939.
 24. Cruz-Filho AM, Sousa-Neto MD, Saquy PC, Pécora JD. Evaluation of the effect of EDTAC, CDTA, and EGTA on radicular dentin microhardness. *J Endod* 2001;27:183-184.
 25. Seidberg BH, Schilder H. An evaluation of EDTA in endodontics. *Oral Surg Oral Med Oral Pathol* 1974;37:609-620.
 26. De-Deus G, Reis C, Paciornik S. Critical appraisal of published smear layer-removal studies: methodological issues. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2011;112:531-543.
 27. Peters OA, Peters CI, Schönenberger K, Barbakow F. ProTaper rotary root canal preparation: effects of canal anatomy on final shape analysed by micro CT. *Int Endod J* 2003;36:86-92.
 28. Taha NA, Ozawa T, Messer HH. Comparison of three techniques for preparing oval-shaped root canals. *J Endod* 2010;36:532-535.
 29. Do Prado M, Simão RA, Gomes BP. Evaluation of different irrigation protocols concerning the formation of chemical smear layer. *Microsc Res Tech* 2013;76:196-200.
 30. Luessen HL, Borchard G, De Boer AG, Junginger HE, Kolter K, Schehlmann V, Sanner A. Use of (meth) acrylic acid/maleic acid copolymers for improving mucosal permeability. USA. US patent 6004575 A. (1999 Dec 21).