

Design and Fabrication of Electrostatic Inkjet Head using Silicon Micromachining Technology

Youngmin Kim*, Sanguk Son*, Jaeyong Choi*, Doyoung Byun**, and Sukhan Lee*

Abstract—This paper presents design and fabrication of optimized geometry structure of electrostatic inkjet head. In order to verify effect of geometry shape, we simulate electric field intensity according to the head structure. The electric field strength increases linearly with increasing height of the micro nozzle. As the nozzle diameter decreases, the electric field along the periphery of the meniscus can be more concentrated. We design and fabricate the electrostatic inkjet heads, hole type and pole type, with optimized structure. It was fabricated using thick-thermal oxidation and silicon micromachining technique such as the deep reactive ion etching (DRIE) and chemical wet etching process. It is verified experimentally that the use of the MEMS inkjet head allows a stable and sustainable micro-dripping mode of droplet ejection. A stable micro dripping mode of ejection is observed under the voltages 2.5 kV and droplet diameter is 10 μm .

Index Terms—MEMS technology, silicon deep etching, electrostatic inkjet head, electrostatic ejection, silicon micro nozzle

I. INTRODUCTION

New advancements in the design and manufacturing process of industrial inkjet head for micro printing are significantly changing the application area of the inkjet printing technology [1-3]. Ink-jet printing technique is

very attractive for forming micro-size patterns for flat panel displays (FPDS), printing circuit board (PCB), semiconductor, biological, optical, and sensor devices due to its low temperature process, direct writing, and rapid photolithography process [4,5].

The inkjet printing mechanisms has been used thermal bubble, piezoelectric and electrostatic method. Thermal and piezoelectric inkjet printing are based on pushing out the liquid in a chamber through a nozzle by actuators, such as thermal bubble and piezoelectric actuators. However, thermal bubble actuator has the heat problem when the array of nozzle make in a large area and piezoelectric actuator is difficult to make droplet smaller than nozzle size [5]. Also, the head consisting of piezoelectric or a heater element has the disadvantage of the complex structure. Electrostatic inkjet are based on protruding through an orifice induced by an electric field forms a meniscus called the Taylor cone [6] and can separate from the meniscus tip as fine droplets much smaller than the orifice diameter. Electrostatic inkjet has a greater advantage than piezoelectric inkjet and thermal inkjet in the ability to eject fine droplets and in the simplicity of structure [7]. Lee et al. [8-9] have been proposing and developing an electrostatic drop-on-demand print head that is capable of overcoming the limitations of piezoelectric and thermal bubble print heads described above. Several researchers studied the electrostatic micro-dripping mode for industrial application. Hiroyuki et al. [10] investigated electrostatic ink jet phenomena in pin-to-plate discharge system. Yuji Ishida et al. [11] demonstrated ink-droplet formation in double-gate electro-spray. The droplet ejection using a needle-type inkjet head was also investigated.

In this paper, we present the analysis and fabrication of the electrostatic inkjet head using the microelectromechanical system (MEMS) technology. First, a micro droplet is

Manuscript received June. 3, 2008; revised June. 10, 2008.

* School of Information and Communication Engineering, SKK Univ., Kyunggi-do, 440-764, Korea

** School of Mechanical and Aerospace Engineering, Konkuk Univ., Seoul, 151-600, Korea

E-mail : lsh@ece.skku.ac.kr, rockeyk@lycos.co.kr

formed from the liquid meniscus due to the induced electric field. The electric field is obtained by solving the Maxwell governing equation. Using the parametric study, we find the optimal shape of the nozzle geometry in a view of enhancing and focusing the electric field near the center of meniscus. Then, the electrostatic inkjet head was fabricated by the thick-oxidation process and the MEMS technology. Finally, the characteristic of drop-on-demand ejection is analyzed using the electrostatic inkjet method and MEMS structure of the nozzle.

II. DESIGN AND SIMULATION

To achieve an effective micro dripping ejection, inkjet head was designed and fabricated to provide concentrated electric force on nozzle and pole tip. Fig. 1 and Fig. 2 show the schematic of the proposed electrostatic inkjet heads of hole type (Fig. 1) and pole type (Fig. 2). This structure consists of reservoir, nozzle and conductive pole to concentrate electric field.

Micro droplet is formed from the liquid meniscus due to the induced electric field. The electric field is obtained by solving the following governing equations.

$$\nabla \cdot \varepsilon \nabla \varphi = -\rho \quad (1)$$

$$\vec{E} = -\nabla \varphi \quad (2)$$

where \vec{E} , φ , ε , and ρ are the electric field vector, the electric potential, the permittivity, and the charge density, respectively. These equations are solved by FEM (finite element method).

Fig. 3 shows the schematic of the proposed electrostatic inkjet head. This structure consists of glass electrode part and nozzle part with a reservoir. The inkjet head utilizes electrostatic forces that act between electrode and nozzle tip. The electrostatic forces are created when a voltage is applied electrode and head bottom. The surface of the inkjet head becomes wet with liquid after applying an electric field. Then charged liquid is separated from the inkjet head tip as fine droplets. When the force induced by an electric field on the inkjet head tip is stronger than the resultant force of surface tension, ink viscosity and conductivity, the meniscus called Taylor cone is generated and fine droplets is separated from the head by Coulomb force.

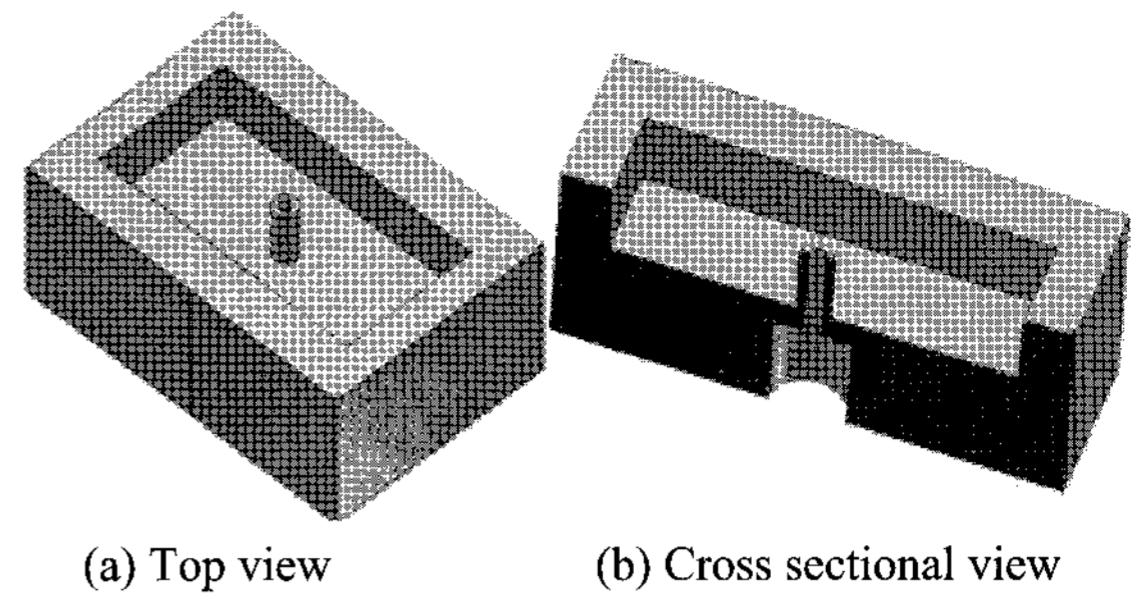


Fig. 1. Schematic of the nozzle part of the proposed hole type electrostatic inkjet head.

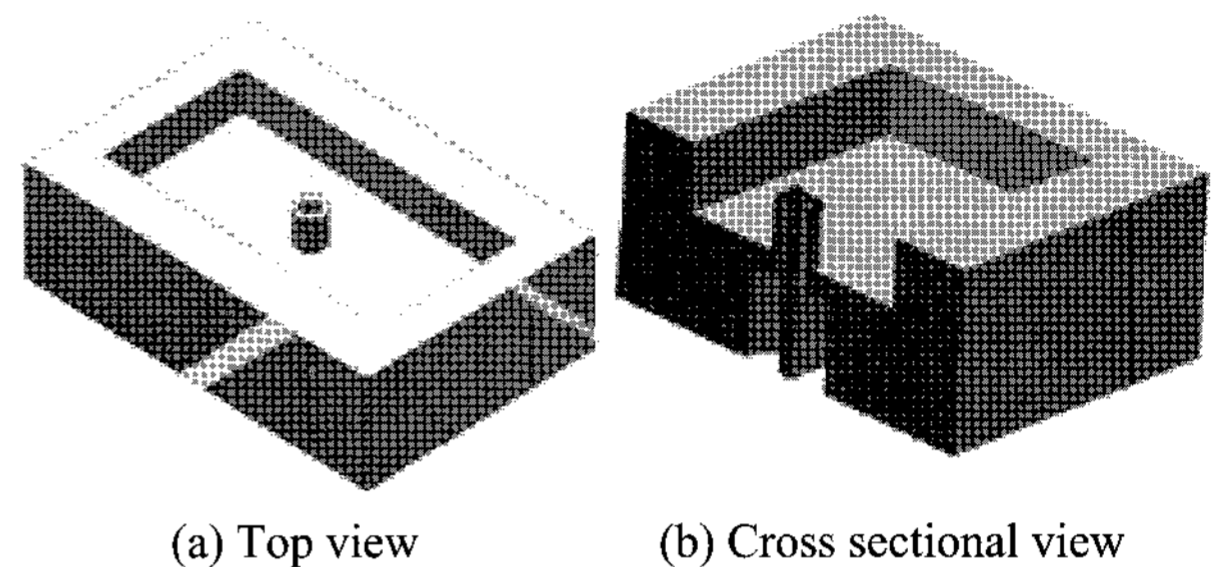


Fig. 2. Schematic of the nozzle part of the proposed pole type electrostatic inkjet head.

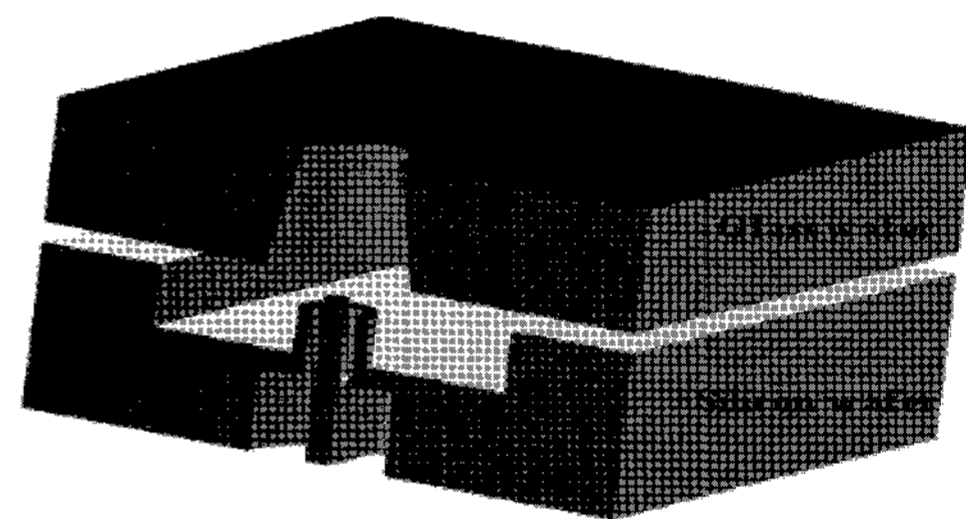


Fig. 3. The structure of the proposed pole type electrostatic inkjet head.

Fig. 4 shows the result of the electric field simulation used the DI water as the liquid solution. Fig. 5 shows the electric field strength as a function of the variation of the nozzle height. The electric field strength increases linearly with increasing height of the micro nozzle. Also, as the height of the nozzle increases, the electric field along the periphery of the meniscus can be more concentrated.

In order to find optimal structure and demonstrate concentration of electrostatic force at the pole edge, we have simulated pole type inkjet head using FEMLAB. Fig. 6 shows the result of the electric field simulation used the DI water as the liquid solution. The structure of the nozzle inner diameter, thickness, and pole diameter are 80 μm , 20 μm and 40 μm , respectively. The pole height is 50 μm . As the result, the concentration of electrostatic force was shown at the conductive pole edge.

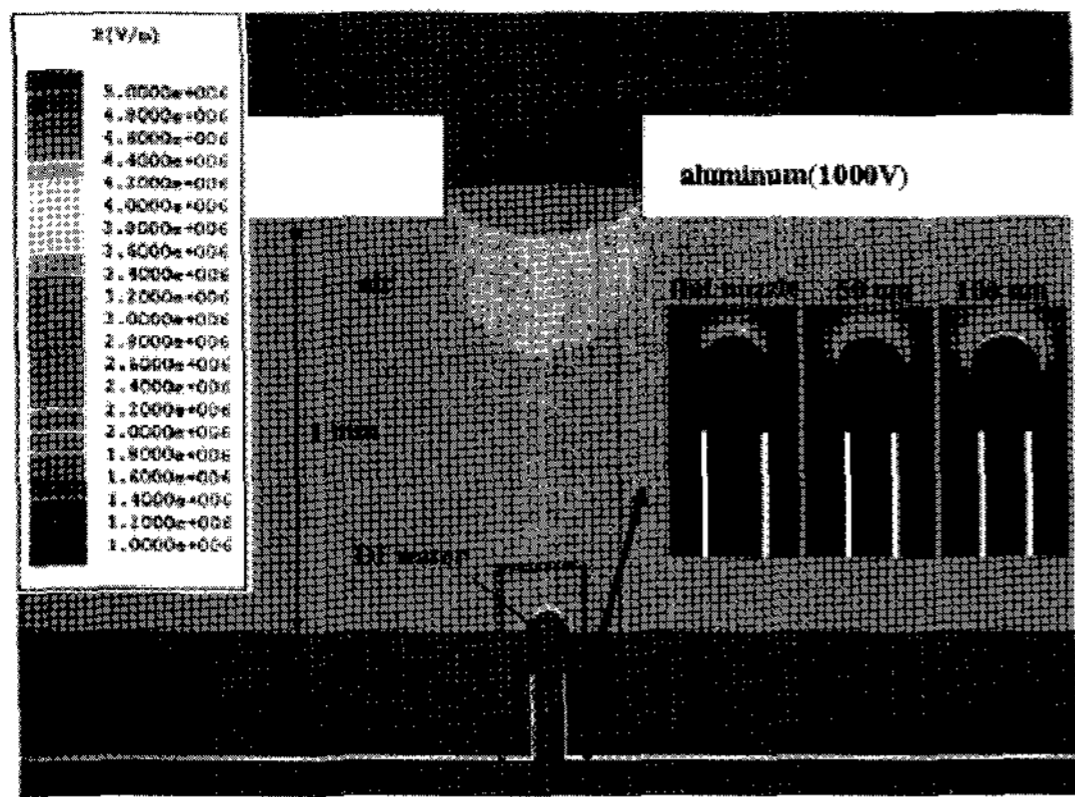


Fig. 4. Electric field simulation of the hole type inkjet head.

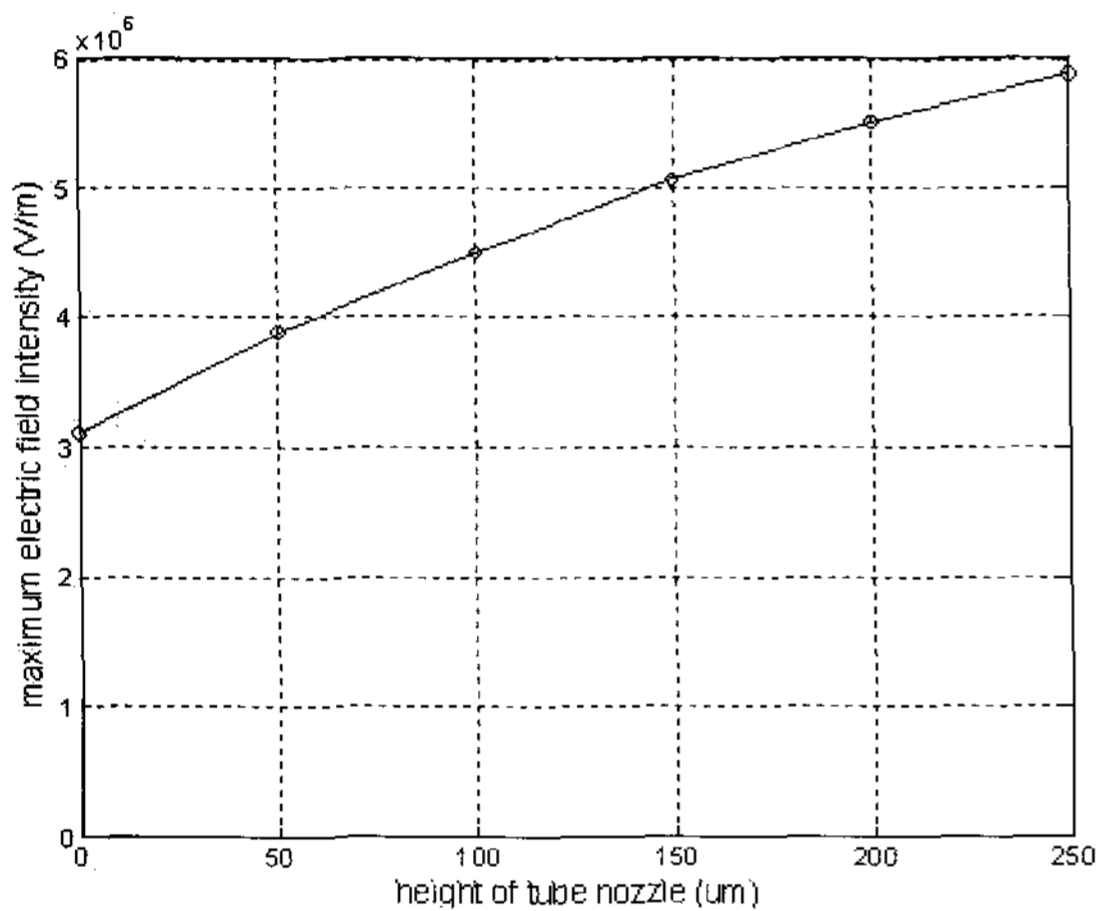


Fig. 5. Electric field strength as a function of the nozzle height of the hole type inkjet head.

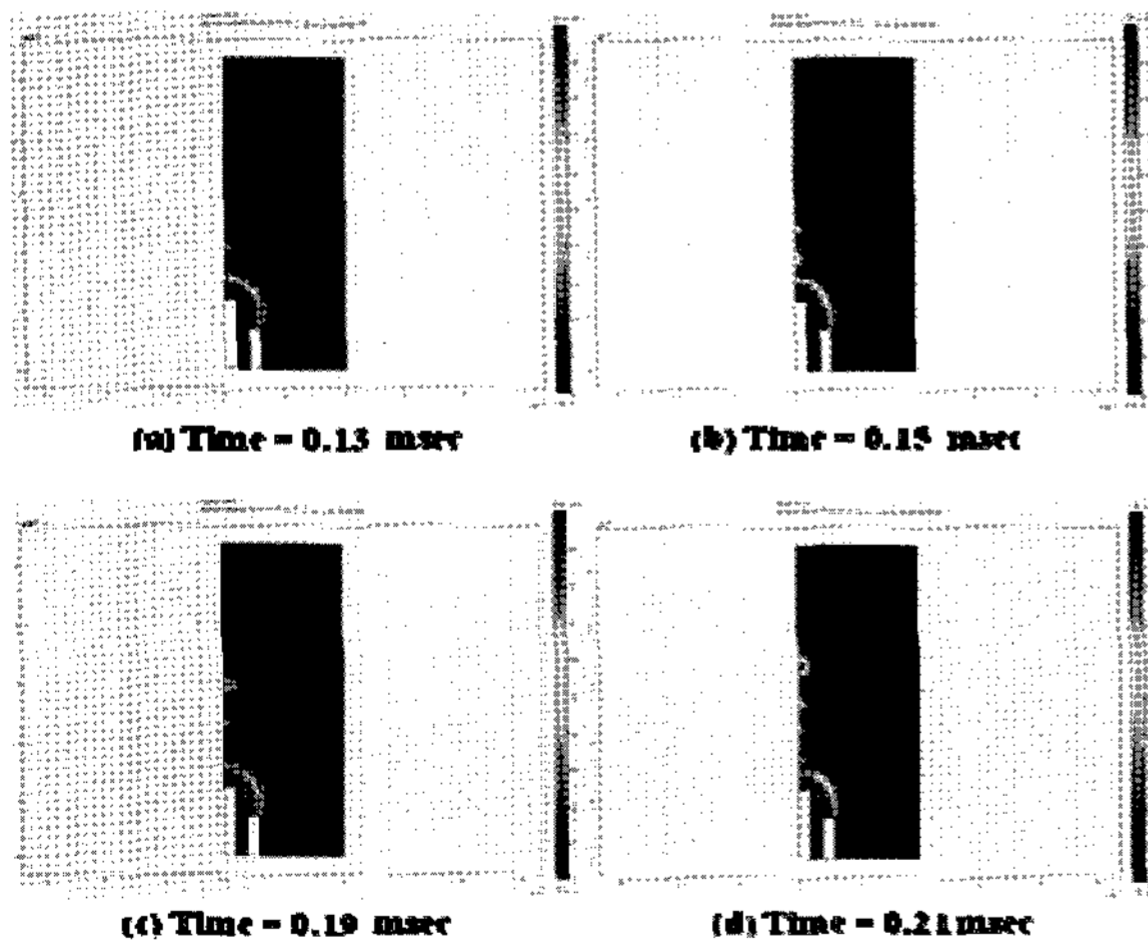


Fig. 6. Electric field simulation as a function of the time variation of the pole type inkjet head.

III. FABRICATION

The proposed electrostatic inkjet head consists of the glass top-layer part and the silicon bottom-layer part.

They are fabricated using thick-thermal oxidation and silicon micromachining technique such as the deep reactive ion etching (DRIE), separately. The top electrode was previously fabricated on glass wafer. The aluminum layer is deposited by sputter on the glass wafer, and then dry film is coated by laminator and patterned the hole of the ink ejection. The electrode of the hole type is formed using the sand blaster.

The fabrication process of the electrostatic inkjet head with the micro nozzle is shown in Fig. 7. The p-type, (100)-oriented double-side silicon wafer substrate is used. First, a thick silicon oxide of 2 μm is thermally grown (Fig. 7(a)). This silicon oxide layer is used as a mask for forming the nozzle and backside reservoir. The front side is patterned by photolithography using the thick positive photoresist. The pole and nozzle for inkjet ejection are formed by oxide dry etching and DRIE (Fig. 7(b)). The depth of the nozzle outer part is about 70 μm. Next, the back side oxide is patterned by photolithography and dry etching (Fig. 7(c)). The reservoir for ink storage is then formed using DRIE (Fig. 7(d)). To penetrate wafer of patterned nozzle, the front side silicon is etched using DRIE (Fig. 7(e)). Finally, the oxide layer of the wafer is etched by the chemical wet etching included HF solution and cleaned before the next process (Fig. 7(f)).

Fig. 8 shows photomicrograph of the nozzle part of electrostatic inkjet head after silicon deep etching. The depth of nozzle outer part is 50 μm. Fig.9 shows photomicrograph of the nozzle part of electrostatic inkjet head inserted the pole. Fabricated head's nozzle inner

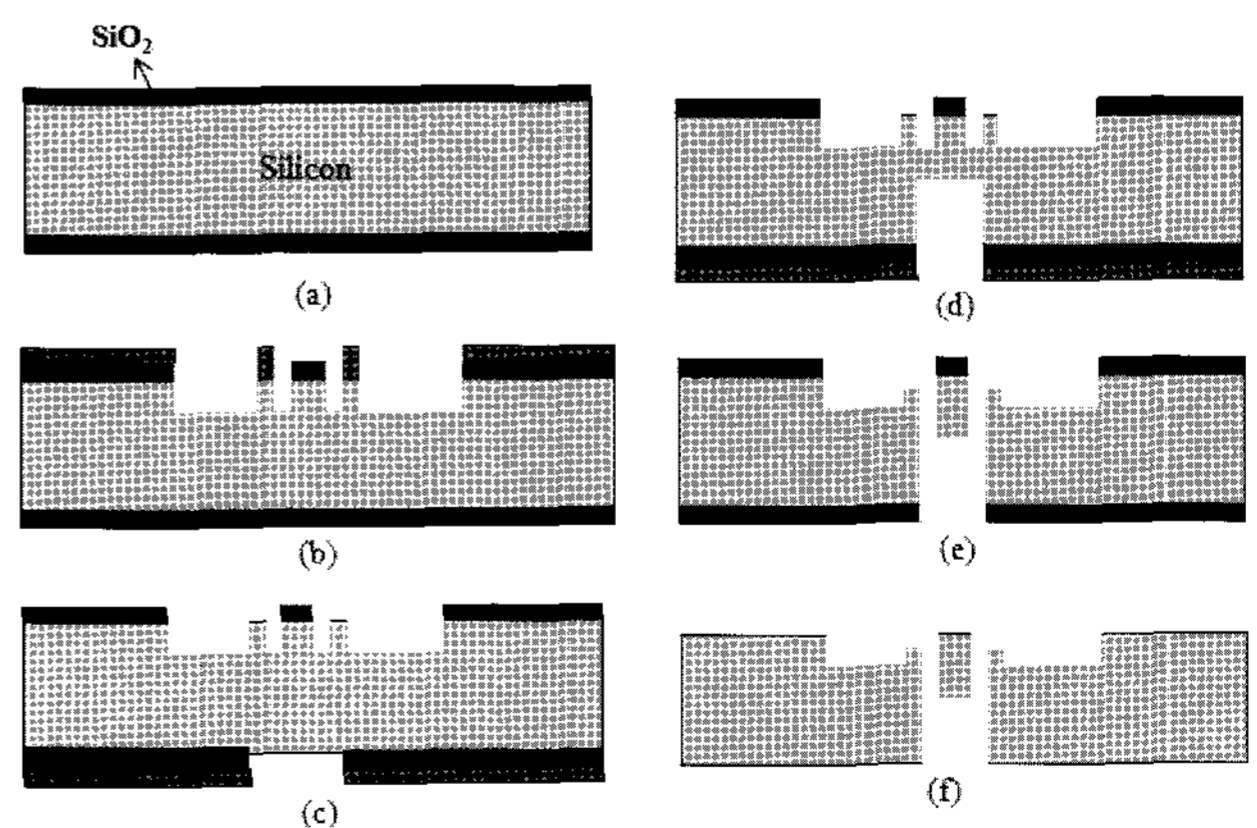


Fig. 7. Fabrication Process : (a) SiO₂ layer on silicon wafer, (b) Oxide(deep Si etch mask) patterning and deep Si etching, (c) reservoir patterning on the bottom silicon wafer, (d) Deep Si etching, (e) Deep Si etching for pole formation, (f) SiO₂ removal by the HF solution.

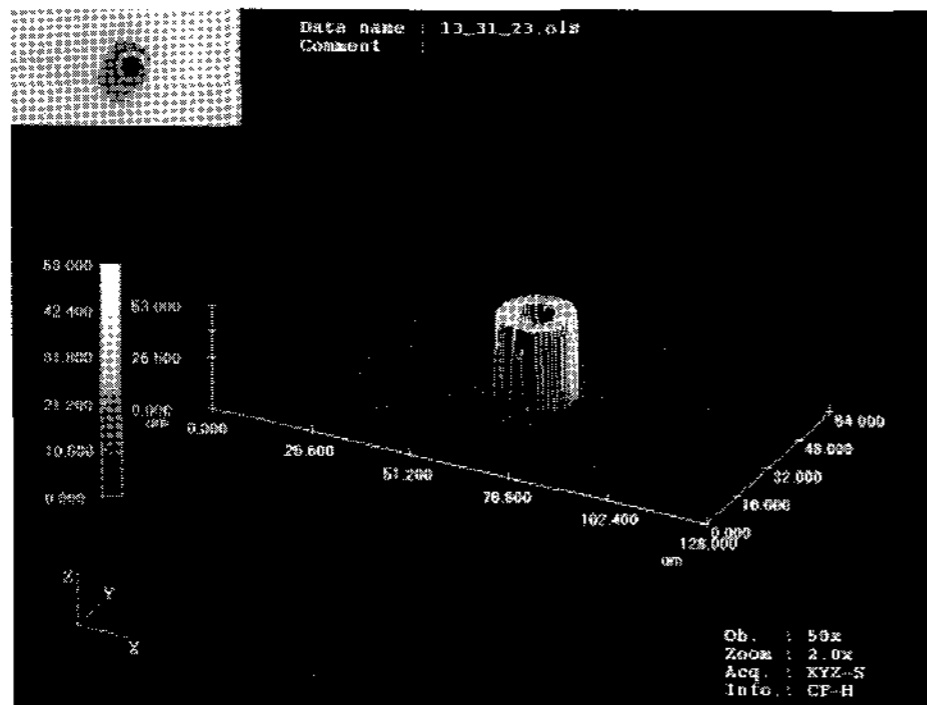


Fig. 8. Photomicrograph of the nozzle part of hole type electrostatic inkjet head after silicon deep etching process.

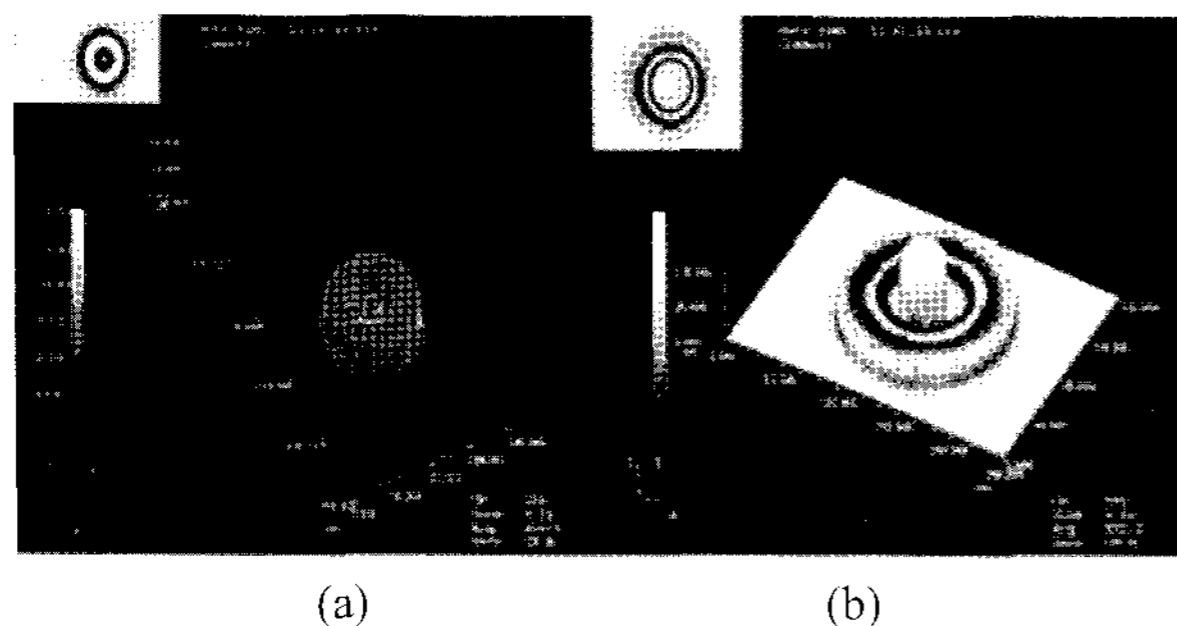



Fig. 9. Photomicrograph of the nozzle part of pole type electrostatic inkjet head, (a) after first, (b) 2nd silicon deep etching process.

diameter, thickness, and pole diameter are $60\ \mu\text{m}$, $20\ \mu\text{m}$ and $20\ \mu\text{m}$, respectively. The depth of nozzle outer part is $70\ \mu\text{m}$. To obtain opened pole, we have performed DRIE process. The etch rate ratio of the etched nozzle has 1 : 1.5. Fig. 9(b) shows photomicrograph of the nozzle part of electrostatic inkjet head after DRIE process of the Fig. 7(e). We measure the fabricated pole using the 3D photomicroscope (LEXT, OLYMPUS Co.) equipment.


Fig. 10 shows the SEM images of the nozzle part of the electrostatic inkjet head after the fabrication process. Fig. 10(a) shows the hole type nozzle fabricated MEMS technology. The inner diameter and outer diameter of the fabricated nozzle are $20\ \mu\text{m}$ and $50\ \mu\text{m}$, respectively. Fig. 10(b) shows the pole type nozzle opened conductive pole of $50\ \mu\text{m}$ to provide concentrated electric force on pole tip. The height of nozzle outer part and pole diameter are $120\ \mu\text{m}$ and $20\ \mu\text{m}$, respectively.

IV. EXPERIMENTAL RESULTS AND DISCUSSION

Fig. 11 shows the schematic of the experimental system for electrostatic inkjet ejection. This system consists of the head system, the high speed camera, micro syringe

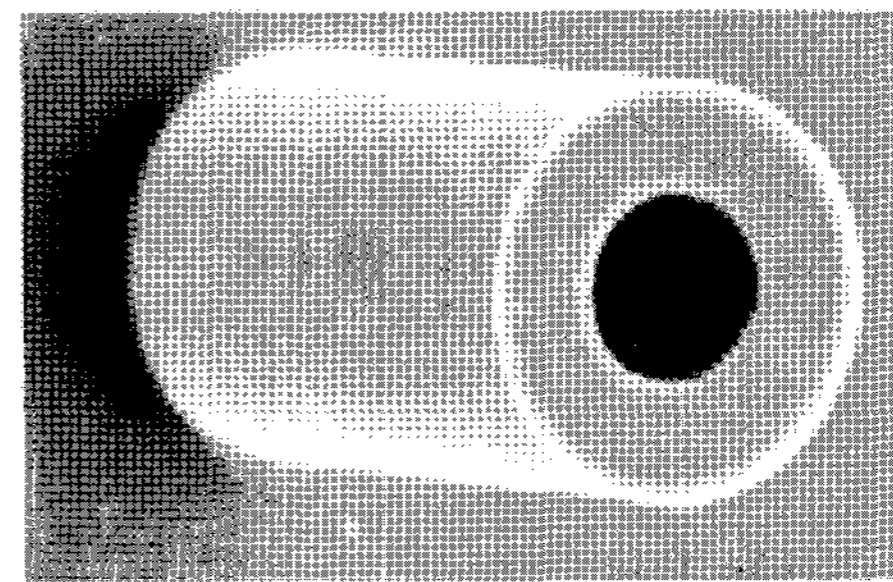

(a)

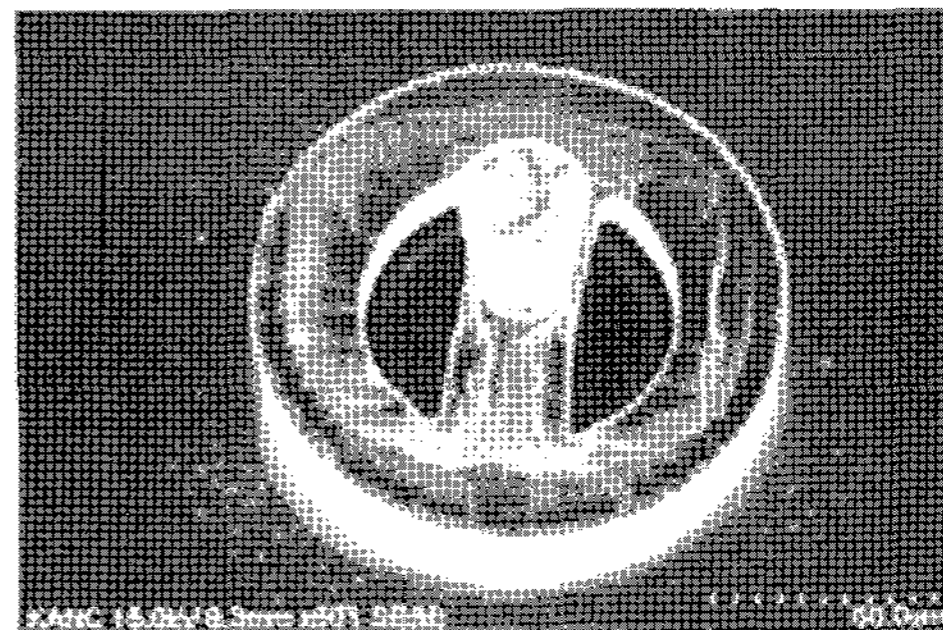

(b)

Fig. 10. SEM images of the nozzle part, (a) of hole type (b) of pole type electrostatic inkjet head.

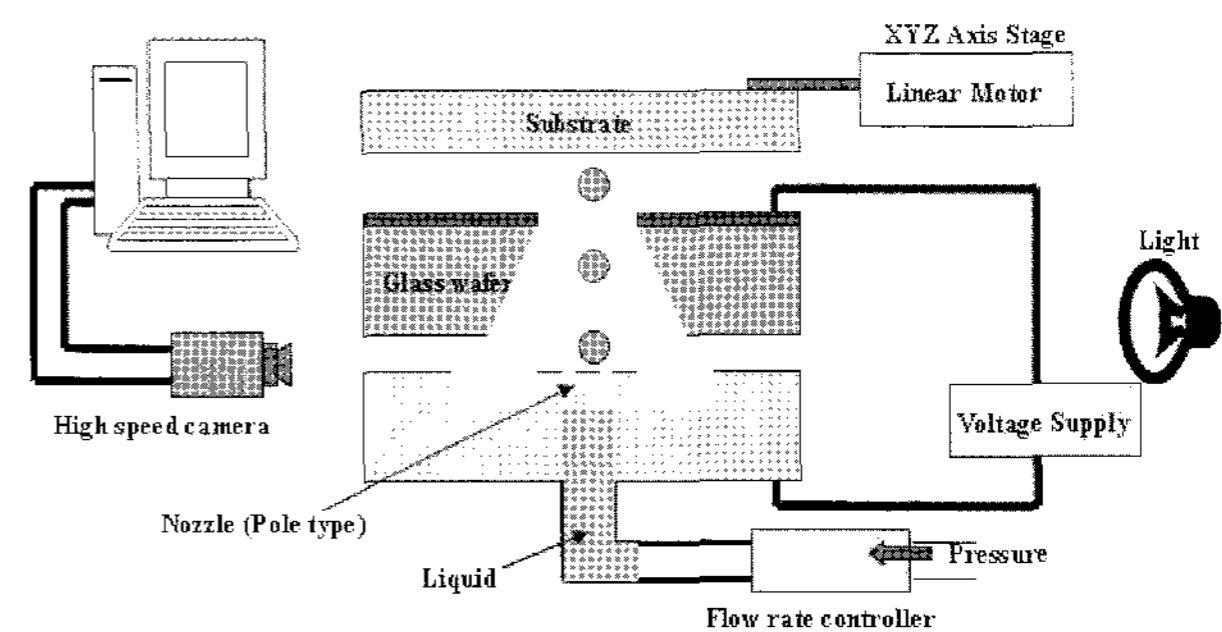


Fig. 11. The schematic of the experimental system.

pump, power, and computer.

A high speed camera (IDT XS-4) with a micro-zoom lens and a halogen lamp was used to visualize droplet ejection. The high speed camera can image 5000 frames per second at a 512×512 resolution with a micro-zoom lens and a LED light source were used. A high voltage power supply (maximum voltage of 3.0 kV) was used with a relay switch to control electrostatic field. The liquid have been supplied to the nozzle with constant velocity by micro syringe pump and the voltage has been provided to the upper electrode.

The jetting mode depends on the applied voltage, the flow rate, and the liquid properties, such as electric conductivity, surface tension, and viscosity. To make an experiment on the micro ejection of the electrostatic inkjet

head, the conductive liquid of the mixture of D2O, SDS, and micelle-suspended Carbon Nano Tube (5 %wt SWNT) solution is used as ink. The outer diameter of the nozzle is 50 μm and the gap between the upper electrode and the nozzle orifice is set about 800 μm . The constant flow rate by a micro pump is kept at 0.1 $\mu\text{l}/\text{min}$.

Fig. 12 shows the series of image frames observed with the high-speed camera showing the micro droplet ejection by the fabricated hole type inkjet head. The supplied voltage is kept at 1.7 kV between the upper Al electrode and the nozzle ground. The droplet diameter ejected from the nozzle tip is measured about 80 μm .

Fig. 13 shows the series of image frames observed with the high-speed camera showing the micro droplet ejection by the fabricated hole type inkjet head. The supplied voltage is kept at 2.5 kV. The droplet diameter ejected from the nozzle tip is measured about 10 μm . Also, a stable micro dripping mode or Cone-jet mode of ejection is observed under the voltages ranged from 1.9 kV to 2.4 kV. These results show that the micro dripping mode of tiny droplet size is observed by experimental system. And, the ejection experiment of the conductive ink using the pole type electrostatic inkjet head is in progress.

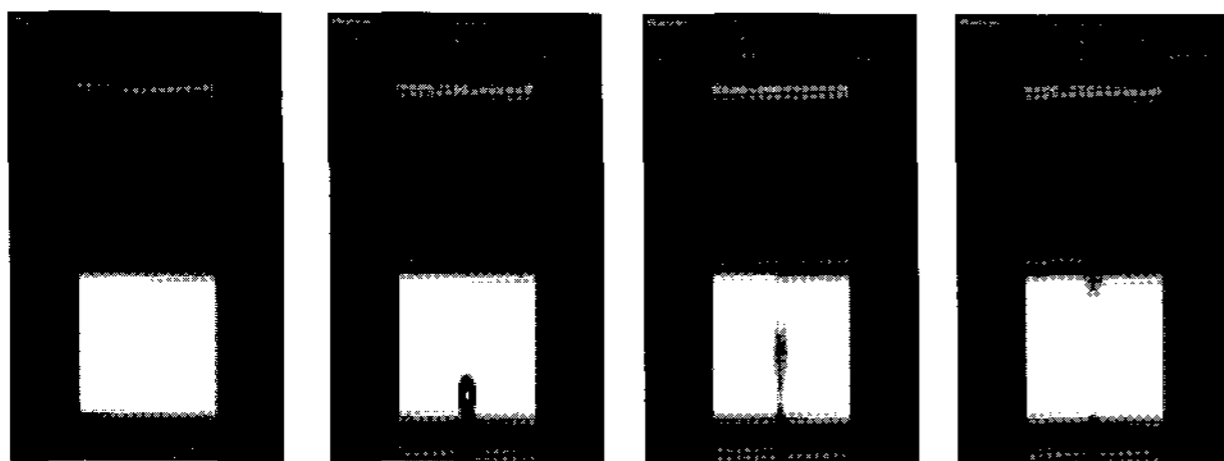


Fig. 12. Images taken with high-speed camera showing event of micro ejection from nozzle of inkjet head.

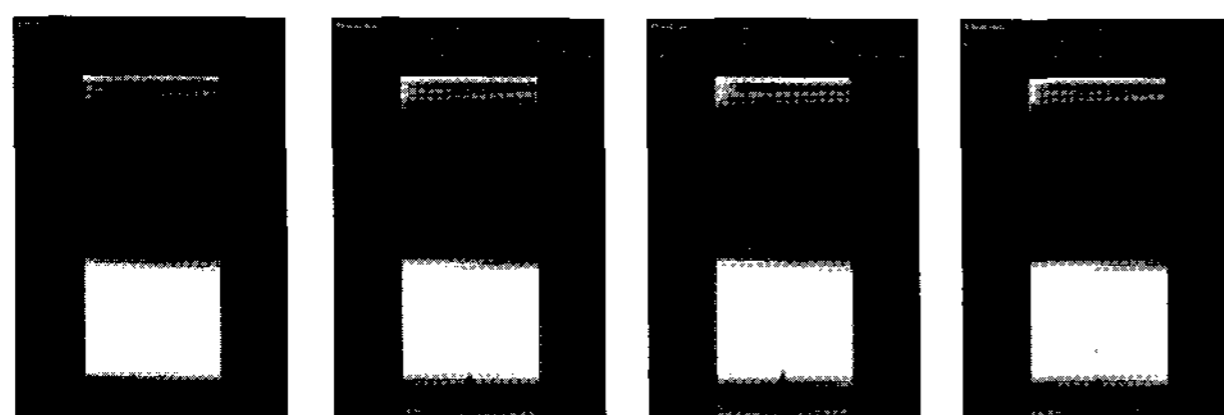


Fig. 13. Images taken with high-speed camera showing event of micro ejection from nozzle of inkjet head.

V. CONCLUSIONS

The hole type electrostatic inkjet head and pole type electrostatic inkjet head with conductive pole inserted in

a silicon nozzle have fabricated using thick-thermal oxidation and silicon micromachining technology. To form silicon nozzle and conductive pole in the silicon nozzle, we used DRIE process.

As a result of pole type inkjet head, Fabricated head's nozzle inner diameter, thickness, and pole diameter are 60 μm , 20 μm and 20 μm , respectively. The height of nozzle outer part and pole diameter are 120 μm and 20 μm , respectively. The height of the conductive pole is about 50 μm . Also, The inner diameter and outer diameter of fabricated hole type nozzle are 20 μm and 50 μm , respectively.

The fabrication process used in this paper was very simple and reproducible. It is expected that this fabrication process can apply for inkjet head of fine pitch and multi-array.

ACKNOWLEDGMENTS

This research was supported by a grant from the Seoul R&BD Program.

REFERENCES

- [1] Yuji Ishida, Kazunori Hakiyai, Akiyoshi Baba and Tanemasa Asano, "Electrostatic Inkjet Patterning Using Si Needle Prepared by Anodization," *Japanese Journal of Applied Physics*, Vol. 44, No. 7B, pp. 5786-5790, July 2005.
- [2] S. Lee, D. Byun, S. J. Han, S. U. Son, Y. J. Kim, H. S. Ko, "Electrostatic Droplet Formation and Ejection of Colloid," *MHS*, July 31, 2004.
- [3] S.U.Son, Y.M.Kim, J.Y.Choi, S.H.Lee, H.S.Ko, and D.Y.Byun, "Fabrication of MEMS Inkjet Head for Drop-on-Demand Ejection of Electrostatic Force Method," *Trans. KIEE*, Vol.56, August, 2007.
- [4] C.M. Ho, "Fluidics-the link between micro and nano sciences and technologies," *IEEE Int. Conf. MEMS*, pp.375-384, 2001.
- [5] E. Lee, CRC Press, *Microdrop Generation*, 2003.
- [6] G. Taylor : *Proc. Roy. Soc. Lond. A*, 313, 1969.
- [7] A. Sou, K. Sasai, and T. Nakajima, "Control of Ink Transportation in Electrostatic Inkjet Printer," *ASME Fluid Engineering Division Summer Meeting*, July 2002.
- [8] Y. J. Kim, H. S. Ko, S. H. Lee, S. U. Son, D. W.

Jung and D. Y. Byun, "Electrostatic droplet ejector with monolithic fabrication of nozzle," *Journal of the Korean Physical Society*, Vol.51, pp.S42~S46, 2007.

- [9] S. H. Lee, D. Y. Byun, D. W. Jung, J. Y. Choi, Y. J. Kim, J. H. Yang, S. J. Han, S. U. Son, S. B. Quang Tran and H. S. Ko, "Pole-type ground electrode in nozzle for electrostatic field induced drop-on-demand inkjet head" *Sensors & Actuators*, Vol. 141, No. 2, pp.506-514, 2008.
- [10] Hiroyuki Kawamoto, Shinjiro Umezu and Ryuta Koizumi, "Fundamental investigation on electrostatic ink jet phenomena in pin-to-plate discharge system," *Journal of imaging science and technology*, Vol 49, 1, pp.19-27, 2005.
- [11] Yuji Ishida, Keigo Sogabe, Kazunori Hakiai, Akiyoshi Baba and Tanemasa Asano, "Properties of Ink-Droplet Formation in Double-Gate Electrospray," *Japanese Journal of Applied Physics*, Vol. 45, No. 8A, pp.6475-6480, 2006.



Youngmin Kim received the BS and MS degrees in electronic engineering from Cheju National University, Cheju, Korea, in 1990 and 1998, respectively and his PhD degree in electronic engineering from Kyungpook National University, Daegu, Korea, in 2004.

From 2005 to August 2006, he worked for SYHITECH Co., Korea, as a Senior Manager of R&D Center, where he has been engaged in research on semiconductor sensors. Since August 2006, he has worked as a BK21 His current research topics are development of electrostatic micro-liquid droplet injector, passive/active control system of liquid flow in micro-system using MHD and biomimetic systems. His research interests include micro-fluidics, MEMS, and biomimetics.




Sanguk Son received the BS, and MS degrees in School of Information and Communication Engineering from the Sungkyunkwan University, Suwon, Korea, in 2003 and 2005, respectively, and is a PhD student in Sungkyunkwan University. His research topic is the electrostatic micro-liquid droplet injector and MEMS fabrication.



Jaeyong Choi received the BS, and MS degrees in School of Information and Communication Engineering from the Sungkyunkwan University, Suwon, Korea, in 2006 and 2008, respectively, and is a PhD student in Sungkyunkwan University. His research topic is the electrostatic micro-liquid droplet injector.



Doyoung Byun received the BS, MS, and PhD degrees in School of Mechanical and Aerospace Engineering from the Korea Advanced Institute of Science and Technology (KAIST), Taejeon, Korea, in 1994, 1996, and 2000, respectively. From 2000 to 2002, he was in the Korea Institute of Science and Technology Evaluation and Planning as a senior researcher. In 2003, he joined the faculty of the Department of Aerospace Engineering, Konkuk University, Seoul, Korea. His current research topics are development of electrostatic micro-liquid droplet injector, passive/active control system of liquid flow in micro-system using MHD and biomimetic systems. His research interests include micro-fluidics, MEMS, and biomimetics.

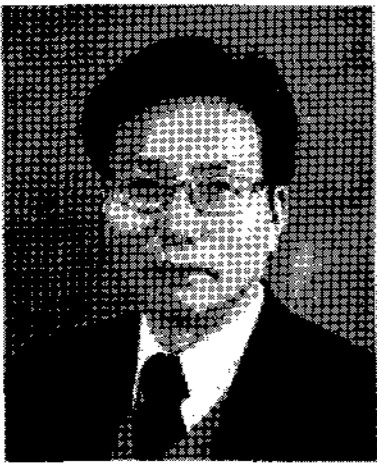

Sukhan Lee is a distinguished professor of information and communication engineering and the Director of the Intelligent Systems Research Center at the SungKyunKwan University (SKKU) since March 2003. Prior to his tenure with SKKU, he has been an Executive Vice President and Chief Research Officer (CRO) of the Samsung Advanced Institute of Technology (SAIT), managing micro- and nano-systems as well as intelligent systems sectors for over 5 years (1998-2003). Dr. Lee has been a professor of electrical engineering and computer science at the University of Southern California (1983-1997) and jointly held a senior research staff position with the Jet Propulsion Laboratory (JPL), California Institute of Technology (1990-1997). Dr. Lee received his PhD from Purdue University, West Lafayette, and MS and BS from Seoul National University. He has been chairing numerous National Committees for developing the S&T policies and R&D plans for Korea, including the National Technology Roadmap (2002), the National R&D Thrusts for Future Economic Growth of Korea (2003), the National Strategy for International R&D Collaboration (2003), and the National Strategy for Intelligent Robot Standardization (2004). He is a Fellow of IEEE and a Member of the Korean Academy of Science and Technology. Dr. Lee is currently directing the Industrial Activities Board as a Vice President of IEEE Robotics and Automation Society. He is the Founding Editor-in-Chief for the Springer-Verlag Journal of Intelligent Service Robotics.